

LABORATORY SCALE BRICK PRODUCTION FROM LEATHER BUFFING DUST TO MANAGE SOLID WASTE IN THE TANNERY

Md. Abul Hashem¹, Tanvir Ahmed², Md. Mutasim Fuad³ and Md. Sabbir Rahman Akash⁴

^{1,2,3,4}Department of Leather Engineering, Khulna University of Engineering & Technology (KUET), Khulna-923, BANGLADESH
Corresponding author: mahashem96@yahoo.com

ABSTRACT

The micro-fined leather buffing dust generates during the buffing operation. The generated leather buffing dust already impregnated various chemicals, syntan, synthetic oils, dyestuff, tanning agents, etc. The byproduct, leather buffing dust is minute in size with less in weight, enabling it to float in the air thus causing significant air, water, and soil pollution being disposed into the environment. The emitted leather buffing dust is harmful to human health. This study aims to use leather buffing dust on a laboratory scale for brick production and evaluate the physicomechanical, environmental, and morphological properties of produced bricks. The bricks were produced conventionally by mixing leather buffing dust in various percentages ranging from 0%, 5%, 10%, 15%, 20%, and 25% (wt.) with clay, and bricks were fired in the muffle furnace at 1000°C. Results indicate that 5% leather buffing dust incorporated fired brick compressive strength was 9.2 MPa and Scanning Electronic Microscope (SEM) image shows a smoother surface structure with no visible porosity. Therefore, 5% leather buffing dust incorporated brick is feasible that will reduce the environmental pollution from the tannery.

Keywords: Chromium, Compressive strength, Environment, Micro-fined fibre, Pollution

INTRODUCTION

Globally, the leather industries that run properly generate 5.4 million tons of solid waste in addition to liquid waste per year (Buljan et al. 2000). Collagen fibres, which are putrescible by nature, are converted using a variety of chemicals to create consumer-ready goods (Swarnalatha et al. 2006). Raw trimmings, limed fleshing, leather trimmings, wet blue trimmings, waste of crust leather, chrome shaving dust, cut-offs of finished leather, and buffing dust are generally considered wastes (Sethuraman et al. 2013). Limed fleshing is the major portion of tannery solid wastes generated from the beamhouse operations of leather processing yielding 50-60% of total solid waste (Kanagaraj et al. 2006). Buffing is the pre-finishing operation where the fleshing side of the leather is buffed to obtain a smooth surface or to make an even thickness (Sundar et al. 2011) even the grain side of the leather is buffed to eliminate defects as much as possible to improve the adhesion of the finished film (Hashem and Nur-A-Tomal, 2018). During the buffing operation, a huge amount of micro-fined collagenous fibres are generated. The generated micro-fined powder might be airborne which causes air pollution. Buffing dust is previously impregnated with chromium, synthetic fat, tanning agents, and dyestuffs (Swarnalatha et al. 2008). Singh and Singh (2003) reported that leather buffing dust is harmful to human health. It causes kidney dysfunction (Love, 1983) and lung cancer (Leonard and Lawverys, 1980). The disposal of generated buffing dust to the environment for landfilling could contaminate land or soil with heavy metals such as chromium. Land co-disposal of the leather buffing dust increases the possibility of leaching, which might enter into the human food chain through various physicochemical or biological reactions.

Many researchers attempted to develop buffing dust disposal methods-thermal incineration, pyrolysis, and bioremediation (Swarnalatha et al. 2008; Chronska and Przepiorkowska, 2008; Emmanuel et al. 2014; Sekaran et al. 1998). It is reported that at 800°C about 40% of trivalent chromium is transformed into hexavalent chromium compounds that are carcinogenic in nature (Sundar et al. 2011). These conventional techniques for getting rid of the solid waste management generated by the tanning industries are not feasible. They are often disposed of on land; other disposal methods include thermal incineration and anaerobic digestion. Such disposal or treatment techniques typically have several drawbacks, including the potential for excessive sand use, the need for large amounts of manpower during handling, which leads to an unhygienic environment, and the possibility that nontoxic trivalent chromium could turn toxic during the thermal incineration process.

The solid waste produced from the leather industries might be used in various types of applications that could exhibit a significant effect, in addition to handling the waste generation. Furthermore, the focus of the recent investigation is enlightened on the regulation of the process of pyrolysis, which gradually oxidizes the inorganic type metals to get a useable product that may be used in the further manufacture of environmentally friendly, lightweight building block material, resulting in the convenient type of management of chromium-containing buffing dust. During the pyrolysis process, the material is heated and the organic content transforms into a carbonaceous substance under a certain inert type of atmospheric condition. i.e., the waste materials which constituted a large amount of organic material are converted to unburnt carbon residues (Yilmaz et al. 2007). At high temperatures, it can be stated that the thermal incineration treatment process of chromium-containing waste as solid or liquid, with a regulated supply of oxygen, makes the pyrolysis process to convert the trivalent chromium to chrome consisting of hexavalent valence (Sethuraman et al. 2013). Therefore, after the precipitation of the chemical toxic chrome(III) ion by the addition of some nanoparticles made of iron, the resulting carbonaceous specimen will be produced as a lightweight cemented block (Singh et al. 2011). This study focuses on management of the solid waste i.e., buffing dust as a building block through brick production.

This study aims to use leather buffing dust on a laboratory scale for brick production and evaluate the effect of buffing dust incorporation into the physicomechanical, environmental, and morphological properties of produced bricks.

MATERIALS AND METHODS

Raw Materials Collection

The buffing dust and clay were collected from SAF Leather Industry, Jashore, Bangladesh, and a brickfield, Khulna, Bangladesh, respectively. The collected buffing dust and clay were sun-dried and oven dried at 105°C for 24 hours. The oven-dried leather buffing dust and clay were ground by a laboratory grinder and sieved.



Figure 1 Ground buffing (a) and ground clay (b)

Fabrication of Brick

The buffing dust was mixed homogeneously with clay at different percentages, i.e. 0%, 5%, 10%, 15%, 20%, and 25% of the total weight of a brick. To facilitate the moulding process water was added.



Figure 2 Ground buffing and clay mixed (a) raw brick (b) and burnt brick (c)

After that, the mixture of buffing dust and clay was put into a wooden forma (20 × 10 × 10 cm³), which was previously prepared and cleaned. Care was taken while making the raw bricks so that no void space is created inside. Later the mixture was demoulded from the wooden forma. In this way, a total number of 18 bricks were prepared. After that, these samples of raw bricks were sun-dried for 1 week. Later these were oven-dried at 105°C for 24 hours. The oven-dried raw bricks were fired in the muffle furnace at 1000°C. Figure 2 depicts the ground clay and leather buffing dust, fabricated raw bricks, and burnt bricks.

Testing of Fabricated Bricks

Fabricated were kept at room temperature for seven days and the bricks' quality was evaluated through physicochemical tests. The compressive strength of fabricated bricks was calculated using the ASTM method (ASTM C, 67-02c, 2002). The bricks were cut into two parts using the laboratory-cutting machine. A part of the bricks' was cemented and kept drying for 3 days. The load at which the bricks were broken was recorded. Figure 3 depicts compressive strength.

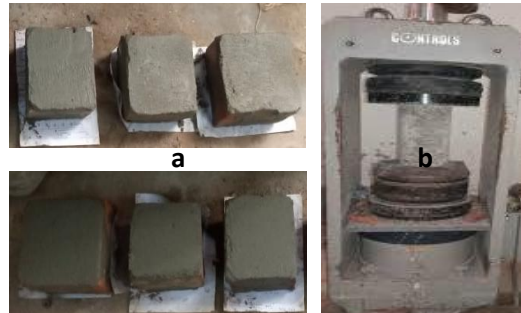


Figure 3 Cementing brick for drying (a) compressive strength test (b)

The compressive strength was calculated by using the following equation:

$$\text{Compressive strength} = \frac{L}{A} \text{ kg/cm}^2 \quad (1)$$

where L is the maximum applied load, A is the cross-sectional area of the bricks.

Weight Loss on Burnt

Before burning, the area of the raw bricks was measured by using a measuring tape. ASTM method (ASTM C326, 1997) served to determine the area shrinkage on burning. After burning, the area of the burnt bricks was again measured by using the measuring tape. The percentage of area shrinkage of the bricks was calculated by using the following equation:

$$\text{Percentage of area shrinkage} = \frac{A_1 - A_2}{A_1} \times 100\% \quad (2)$$

where A_1 is the area of the raw bricks and A_2 is the area of the burnt bricks.

SEM Image

For investigating the morphological structure of the fired bricks SEM (JSM-6610LV) analysis was performed. The accelerating voltage was 15 kV and 1000X magnification was done to obtain the SEM images.

Results and Discussion

Compressive strength

Figure 4 represents the compressive strength of the fabricated brick incorporated with leather buffing dust. It is an important quality for construction materials like brick, as it has to withstand severe loads during construction. It is perceived from Figure 4 that the compressive strength of leather buffing dust brick varies on the percentages of leather buffing dust and clay mixture. It seems that the compressive strength for 0% (only clay), 5%, 10%, 15%, 20%, and 25% leather buffing dust incorporated was 12.4, 9.20, 8.21, 3.12, 2.79, and 2.07 MPa, respectively.

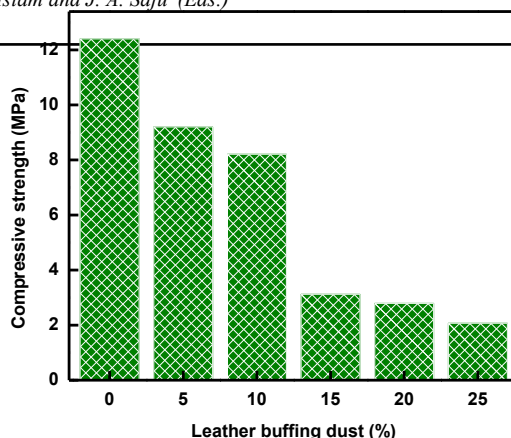


Figure 4 Compressive strength of leather buffing dust incorporated fired brick

It is noticeable that with increasing the incorporation of leather buffing dust, the compressive strength of the fabricated bricks gradually decreased. It seems that by increasing the leather buffing dust percentages in the mixture, the compressive strength was decreased. The decline of the compressive strength could be due to the gradual increase of the percentage of leather buffing dust in the mixture and the bonding ability between them. The compressive strength of the brick mainly depends on the nature and amalgamation of raw materials (Hasan et al. 2022).

Table 1 Standard minimum compressive strength based on different standards (Rukijkanpanich and Thongchai, 2019)

International standard	Minimum compressive strength (MPa)	Brick classification	References
Brazilian Standard	1.5	Clay bricks	NBR 6064 (ABNT, 1983a)
Hollow concrete blocks	3.5-15	Grade A	IS 2185-1, 2005
	3.5-5.0	Grade B	
Common burnt clay bricks	4.0-5.0	Grade C	IS1077, 2007
	3.5-35	Burnt clay bricks	
Hollow clay bricks	3.5	Hollow bricks	IS3952, 2006
Concrete masonry units	5.5	Hollow load-bearing	IS 2185-2, 1983
	4.0	Hollow load-bearing	
	3.5	Hollow non-load bearing	
	10.8	Solid load-bearing	
	7.0	Solid load-bearing	
Concrete Block	11.6 down to 2.1	Grade A Grade B	Standard (TZS 283, 2002(E))

This study implied that the compressive strength obtained with incorporated leather buffing dust is quite compared to different standards (Rukijkanpanich and Thongchai, 2019). It is also clear from Table 1 that 5% to 10% leather buffing dust incorporated fabricated brick can be used for different purposes. Hence, it can be summarised that a significant percentage of leather buffing dust is feasible in brick fabrication.

SEM Images

Figure 5 implies the SEM images for controlled fired brick and 5% leather buffing dust incorporated fired brick. The microstructure of the control brick revealed that the inner surface is not smooth but coarser than buffing dust-incorporated brick. The bonds among the clay particles seemed to be segregated on the inner surface. This indicates the presence of cavities and porosity in the control brick. Instead, 5% leather buffing dust incorporated brick showed a smoother surface structure with no visible porosity. There is less apparent porosity in 5% leather buffing dust incorporated fired brick. Therefore,

5% leather buffing dust incorporated brick is feasible that will reduce the environmental pollution from the tannery.

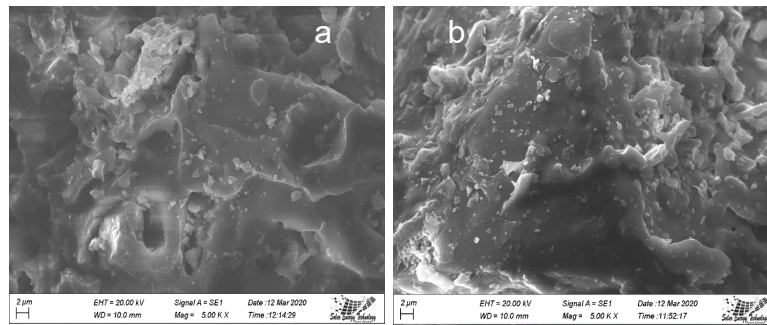


Figure 5 SEM images of controlled (a) and 5% leather buffing dust incorporated fired brick (b)

Implications of the Study

Worldwide, the tanning industry is one of the polluting industries. Bangladesh earns huge amounts of foreign currency from the leather sector. Swarnalatha et al. (2008) reported that per ton of raw hide/skin processing 2-6 kg of buffing dust is generated. It is estimated that 1.7×10^5 - 5.1×10^5 kg of buffing dust is produced in Bangladesh and most cases, this huge amount of buffing dust is dumped into the environment without proper treatment (Hashem and Nur-A-Tomal, 2018). Therefore, from the generated large amount of leather buffing dust, per year Bangladesh could produce a significant number of bricks. Moreover, this huge amount of buffing dust will not be discharged to the environment but rather will be utilized which will reduce the pollution load and enhance the management of solid waste.

CONCLUSION

This study reveals that a fraction of leather buffing dust could be replaced by clay for brick production. The leather buffing dust was mixed with leather buffing dust at percentages of 0%, 5%, 10%, 15%, 20%, and 25% for brick production. The maximum compressive strength was obtained at 9.20 MPa for 5% leather buffing dust. Increasing the leather buffing dust gradually compressive strength was decreased. The addition of leather buffing dust in brick production could be an alternative raw material for the brick industry thus reducing the pollution load generated by the leather industry.

ACKNOWLEDGEMENT

The authors are grateful to the Department of Leather Engineering, KUET for providing the necessary support and personnel. The authors are also thankful to SAF Leather Industries Limited, Jashore, Bangladesh for providing the leather buffing dust sample to conduct the research work.

REFERENCES

- ASTM C, 67–02c (2002) Standard test methods for sampling and testing brick and structural clay tile, American society for testing and materials, West Conshohocken, Pennsylvania, USA.
- ASTM C326 (1997) Test method for drying and firing shrinkage of ceramic white ware clays, American Society for Testing and Materials, West Conshohocken, Pennsylvania, USA.
- Buljan, J., Reich, G., Ludvik, J. 2000. Mass balance in leather processing, US/RAS/92/120, Regional program for pollution controlling the tanning industry.
- Chronska, K., Przepiorkowska, A. 2008. Buffing dust as a filler of carboxylated butadiene-acrylonitrile rubber and butadiene-acrylonitrile rubber, *J Hazard Mater*, Vol. 151, pp. 348-355.
- Emmanueul, S.D., Adamu, I.K., & Ejila, A. 2014. Characterization of chrome buffing dust (CBD) generated from NIL- EST tannery associated with pathogenic fungi, *J Toxicol Environ Health Sci*, 6, 89–98.
- Hashem, M.A., Nur-A-Tomal, M.S. 2018. Tannery solid waste valorization through composite fabrication: A waste-to-wealth approach, *Environ Prog Sustain Energy*, <https://doi.org/10.1002/ep.12860>

- Hasan, M.A., Hashem, M.A., Payel, S. 2022. Stabilization of liming sludge in brick production: A way to reduce pollution in tannery, *Constr Build Mater*, Vol. 314, 125702. <https://doi.org/10.1016/j.conbuildmat.2021.125702>
- Kanagaraj, J., Valappan, K.C., Babu, N.K.C., Sadulla, S. 2006. Solid waste generation in the leather industries and its utilization for cleaner environment-a review, *J Sci Ind Res*, Vol. 65, pp. 541-548.
- Leonard, A., Lawverys, R.R. 1980. Carcinogenicity and mutagenicity of chromium. *Mutat Res*, Vol. 76, pp. 227-239.
- Love, G. 1983. Chromium-biological and analytical considerations. In: Burrows D (ed.) Chromium: metabolism and toxicity. CRC Press, Boca Raton.
- Rukijkanpanich J, Thongchai N (2019) Burned brick production from residues of quarrying process in Thailand. *J Build Eng*, 25, 100811. <https://doi.org/10.1016/j.jobe.2019.100811>
- Sekaran, G., Shanmugasundaram, K.A., Mariappan, M. 1998. Characterization and utilisation of buffing dust generated by the leather industry, *J Hazard Mater*, Vol. 63, pp. 53-68.
- Sethuraman, C., Srinivas, K., Sekaran, G. 2013. Double pyrolysis of chrome-tanned leather solid waste for safe disposal and product recovery. *J Sci Ind Res*, Vol. 4(11), pp. 61-67.
- Singh, I.B., Singh, D.R. 2003. Effects of pH on Cr-Fe interaction during Cr(VI) removal by metallic iron, *Environ Sci Technol*, Vol. 24, pp. 1041-1047.
- Singh, R., Misra, V., Pratap, R. 2011. Synthesis, characterization and role of zero-valent iron nanoparticle in the removal of hexavalent chromium from chromium-spiked soil, *J Nanoparticle Res*, Vol. 13, pp. 4063-4073.
- Swarnalatha, S., Ramani, K., GeethaKarthi, A., Sekaran, G. 2006. Starved air combustion—solidification/stabilization of primary chemical sludge from a tannery. *J Hazard Mater*, Vol. 137, pp. 304-313.
- Swarnalatha, S., Srinivasulu, T., Srimurali, M., Sekaran, G. 2008. Safe disposal of toxic chrome buffing dust generated from leather industries. *J Hazard Mater*, Vol. 150, pp. 290-299.
- Sundar, V.J., Raghavarao, J., Muralidharan, C., Mandal, A.B. 2011. Recovery and utilization of chromium-tanned proteinous wastes of leather making: A review, *Crit Rev Environ Sci Technol*, Vol. 41, pp. 2048–2075.
- Yilmaz, O., Kantarlil, C., Yuksel, M., Saglam, M., Yanik, J. 2007. Conversion of leather wastes to useful products, *J Resour Conserv Recycl*, Vol. 49, pp. 436-448.